

STRENGTH AND DURABILITY ASPECTS OF RECYCLED AGGREGATE CONCRETE

S. Gangaram¹, V. Bhikshma², M. Janardhana³

¹Research Scholar, Jawaharlal Nehru Technological University, Hyderabad, Telangana, India

²Professor of Civil Engineering, University College of Engineering, Osmania University, Hyderabad, Telangana, India

³Professor of Civil Engineering, Jawaharlal Nehru Technological University Hyderabad, Telangana, India

Abstract

The increasing difficulty in securing natural coarse and fine aggregates for the production of concrete coupled with the environmental issues and unlimited extraction of natural aggregates makes the usage of recycled aggregate concrete (RAC) is the prime importance to protect the planets future. However the full use of the material can be justified only through structural applications. Engineers are reluctant to use RCA in structural applications due to lack of design information. In this article, attempt has been made to investigate the strength and durability aspects of Recycled Aggregate Concrete (RAC). Basic characteristics of recycled aggregates were determined in the laboratory. Concrete of M_{20} , M_{30} , and M_{40} , M_{50} , M_{60} and M_{70} grades were designed. The properties of fresh and hardened recycled aggregate concrete were evaluated. The results of compressive strength test, split tensile strength, flexural strength, and permeability tests are presented in this paper.

Keywords: Sustainable Buildings, durability, Recycled Aggregates, Structural Design, Design Codes, Compressive strength, flexural strength, splitting tensile strength.

1. INTRODUCTION

The increasing number of concrete buildings being demolished, the difficulties of disposing of concrete rubble produced together with a developing scarcity of aggregate need to the major urban areas has prompted an interest in the possibility of using concrete rubble as aggregate in concrete. Due to rapid growth in construction industry, continuous depletion found in natural resources which has severe impact on environment. As per the statistics of the World Bank published in Enaadu Telugu news paper, the Delhi 58750 KN and Mumbai 53900 KN are generating daily waste, and ranked 9 and 10 among top ten cities in the World. India has 4th place in the World for generation of daily waste material. As per the World Bank report, Delhi (58750KN), Mumbai (53900 KN), Chennai (26690 KN), Hyderabad (21910 KN), Bangalore (16780 KN), Ahmadabad (13020 KN), Kanpur (10970 KN), Agra (6500 KN) and Indore (5600 KN) are the few cities in India which generate daily wastes. It is worthy to mention that, 50% is the building rubble in daily waste. In this context investigation on strength and durability of recycled aggregate concrete has significant role to use waste material as aggregate.

2. EXPERIMENTAL WORK

Six different mixes were considered in this experimental investigation. Properties of cement, fine aggregate, natural and recycled aggregates were investigated. For all the six mixes, 100% recycled aggregates were considered.

3. MATERIALS

3.1 Cement

Ordinary Portland cement of 53 grade conforming to IS: 12269 were used. It was tested for its physical properties as per IS: 4031(part-II)-1988. And specific gravity and fineness are found to be 3.15 and 3.10.

3.2 Fine Aggregates

Fine aggregate obtained from local market was used. The physical properties of fine aggregate such as specific gravity, fineness modulus was determined in accordance with IS: 2386-1963. Specific gravity and fineness modulus of fine aggregate were found to be 2.56, and 2.95.

3.3 Coarse Aggregates

Recycled aggregates were obtained from random samples of different grades and ages from laboratory waste. Recycled aggregate of max 20mm was used. Specific gravity of recycled coarse aggregate is 2.727. The water absorption capacity of natural aggregates and recycled aggregate in the mixture represents one of the main differences between recycled and natural aggregate. The water absorption values of natural and recycled aggregates were found to be 0.50% and 2.61%.

3.4 Water

Potable water which is free from chemicals and organic materials was used for the study.

4. MIX PROPORTIONING

The mix design was done as per IS: 10262 (2009) for M₂₀, M₃₀, and M40, M₅₀, M₆₀ and M₇₀ with Entroy and shock lock method. The grade of concrete adopted for this study is M₂₀, M₃₀, and M40, M₅₀, M₆₀ and M₇₀. Maximum size of aggregate taken is 20mm and grading of sand is zone II. Different water cement ratios adopted for various concrete mixes and mix proportion was carried out for a slump of 100 ± 25 mm. The quantity of materials required for 1m³ of conventional M₂₀, M₃₀, and M40, M₅₀, M₆₀ and M₇₀ concrete mix are given Table 4.

5. SPECIMEN PREPARATIONS

150x150x150 mm cubes, 100x100x500mm beams and 300 x150 mm diameter cylinder specimens were cast to determine the compressive strength, flexural strength and splitting tensile strength of the concretes. All specimens were cast in steel molds and compacted by using mechanical vibration. After casting, the specimens were cured in air for a period of 24 h, and then removed from mold. The specimens were cured for 7 and 28 days in a water tank at normal temperature.

6. TESTS ON FRESH AND HARDENED CONCRETE

6.1 Fresh Properties

Fresh properties of concrete studied on

- Slump test
- Compaction factor test.

Slump test and compaction factor tests were done on fresh concrete to test the consistency of fresh concrete.

6.2 Mechanical Properties on Hardened Concrete

The mechanical properties of concrete were investigated on

- Compressive strength
- Flexural strength
- Splitting tensile strengths
- Permeability test

After curing, the cubes and cylinder specimens were tested in the compression testing machine. Third point loading method is used for testing beams. Cubes were tested at 7 and 28 days. Cylinders and beams were tested at 28days. Three specimens were considered per each test at 7 and 28days age of concrete.

7. TEST RESULTS OF VARIOUS MIXES

Recycled Aggregate Concrete Mix: Using the mix proportions recycled aggregate concrete of grade M₂₀, M₃₀, M₄₀ and M₅₀ M₆₀ and M₇₀ mixes as given in table 4, the mixes were prepared and tested on fresh and hardened properties of concrete. Results are tabulated below.

7.1 Slump Test

Showed a slump of 75-100mm for all the six mixes

7.2 Compaction Factor Test

Compaction factor value for all the six mixes were between 0.91-0.76.

7.3 Compressive Strength

The compressive strength results are presented in Table 5. Each presented value is the average of three measurements. It is shown in Fig.1, that compressive strength of RAC is not achieved for M₄₀ and above grades. The concrete mixtures prepared with 100 % replacement of RA had a decrease of the compressive strength at 28-day for M₄₀ and above grades of concrete. RAC could not achieve target strength for M₄₀ and above grades of concrete. The higher compressive strength may be attributed to the greater bonding force and strength when similar types of aggregates were used. Normally as RA replacement increased, compressive strength will decrease (Topcu and Sengel (2004) and Kou, Poon and Chan (2007)).

7.4 Flexural Strength

Flexural strength of plain recycled concrete (PRC) beams was investigated for different grades of concrete. Experimental results tabulated below.

7.5 Splitting Tensile Strength

Splitting tensile strength of plain recycled concrete (PRC) specimens was investigated for different grades of concrete. Experimental results tabulated below.

7.6 Permeability Test

Continuous uniform pressure applied @ 78.40N and the permeability of recycled concrete is more compared to the natural aggregate concrete, further; change in fraction of aggregates may improve the permeability characteristics of recycled aggregate concrete.

From table 4, the compressive strength of M₂₀ & M₃₀ grade concretes were achieved target strengths and M40 and above grades were not achieved. Further, to achieve target strength for above M40 & above grades; the fraction of aggregates may be changed. Also flexural and splitting tensile strength values can be improved by changing fraction of aggregate for M40 & above grades.

8. MIX WITH REPLACEMENT OF NATURAL COARSE AGGREGATES WITH RECYCLED COARSE AGGREGATES

Different mixes were made by replacing 100% of natural coarse aggregates with recycled coarse aggregates. Mixes were tested for fresh properties and mechanical properties. Results are tabulated below. Fig 1, Variation of compressive strength at 28days for different grades of concrete mixes is

shown. Fig2. Variation of flexural strength at 28days for different grades of concrete mixes is shown. Fig 3. Variation of splitting tensile strength at 28days for different grades of concrete mixes is shown. From table 4, 5 & 6 figs 1, 2, 3, though splitting tensile strength values at 28days were less, compressive and flexural strength values at 28 days are more for RA compared with target strength of M₂₀ & M₃₀ grades of concrete. So, for further test 100% of NA can be replaced with different fraction recycled coarse aggregates.

9. CONCLUSION

Based on this experimental study, the following conclusions are drawn.

When workability of recycled coarse aggregates was tested using slump test and compaction factor test, the mix shows not adequate workability.

Compressive strength, flexural strength and splitting tensile strength values of concrete mix with recycled aggregates were less for M₄₀ and above grades compared with their target strength.

The study shows that 100% replacement of recycled coarse aggregates for natural aggregate gives satisfactory strength for M₂₀&M₃₀. So the replacement is of much benefit and shall be encouraged to achieve higher grades of concrete.

REFERENCES

- [1] M.L. Berndt, "Properties of sustainable concrete containing fly ash, slag and recycled concrete aggregate", Construction and Building Material, 2009
- [2] Vlastimir Radonjanin , Mirjana Malesev , Snezana Marinkovic , Ali Emhemed Saed Al Maltay "Green recycled aggregate concrete", Construction and Building materials ,2013
- [3] Khaldoun Rahal , "Mechanical properties of concrete with recycled coarse aggregate", Building and Environment ,2007
- [4] Amnon Katz, "Properties of concrete made with recycled aggregate from partially hydrated old concrete", Cement and concrete research, 2003
- [5] IS 10262 – 2009, Concrete mix proportioning – Guidelines, Bureau of Indian standard, July 2009, New Delhi.
- [6] M.S Shetty, "Concrete technology, theory and practice", Revised edition, S chand and company Ltd, 2005.
- [7] A.M. Neville, "Properties of Concrete", fourth edition, Ninth Impression 2011, Pearson(India) Ltd.

Table 1. Properties of cement

Name of test	Result
Specific gravity	3.15
Standard consistency	34%
Initial setting time	40 minutes

Table 2. Material properties of fine aggregates

Name of test	Test Results
Specific gravity	2.74
Water Absorption (%)	0.8
Water content (%)	3.1
Bulk Density (kg/l)	1.73
Percentage Voids (%)	38.73

Table 3. Quantity of materials

Material	Quantity(kg/m ³)					
	M ₂₀	M ₃₀	M ₄₀	M ₅₀	M ₆₀	M ₇₀
Cement	370.00	424.00	475.00	490.00	588.00	565.00
Fine aggregate	673.83	656.00	655.30	491.00	477.50	424.00
Coarse aggregate	111.20	1082.00	1081.40	1252.50	1170.00	1271.00
Water	185.00	186.60	171.00	176.40	188.20	169.50

Table 4. Compressive strength

Design Mix	Compressive strength(Mpa)	
	7-days	28-days
M ₂₀	20.70	36.00
M ₃₀	24.89	40.74
M ₄₀	28.89	32.74
M ₅₀	26.52	30.37
M ₆₀	24.00	37.18
M ₇₀	46.96	46.81

Table 5. Flexural strength

Design Mix	Flexural strength(Mpa)
	28days
M ₂₀	3.182
M ₃₀	3.036
M ₄₀	3.686
M ₅₀	3.832
M ₆₀	3.734
M ₇₀	4.198

Table 7. Permeability test

Design Mix	Permeability of coefficient(m/s)
M ₂₀	1.25 x10 ⁻⁵
M ₃₀	1.79 x10 ⁻⁵
M ₄₀	1.72 x10 ⁻⁵
M ₅₀	1.90 x10 ⁻⁵
M ₆₀	1.17 x10 ⁻⁵
M ₇₀	1.11 x10 ⁻⁵

Table 6. Splitting tensile strength

Design Mix	Splitting strength(Mpa)
	28-day
M ₂₀	1.792
M ₃₀	2.163
M ₄₀	2.281
M ₅₀	2.781
M ₆₀	2.901
M ₇₀	2.789

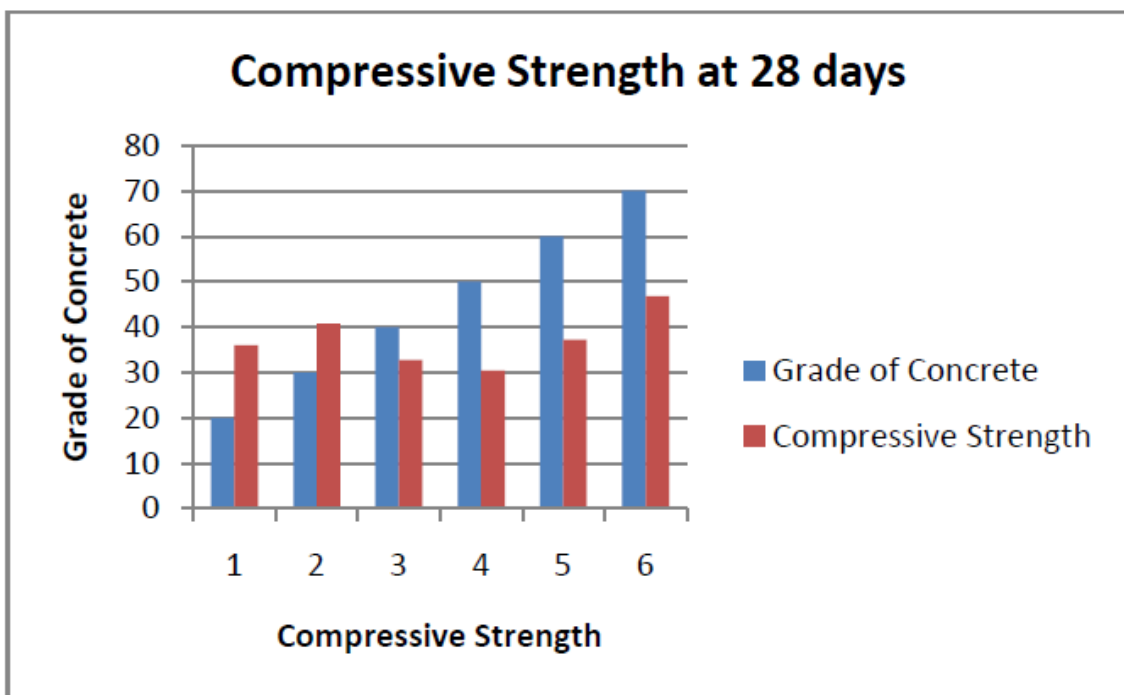


Fig 1. Variation of compressive strength at 28days

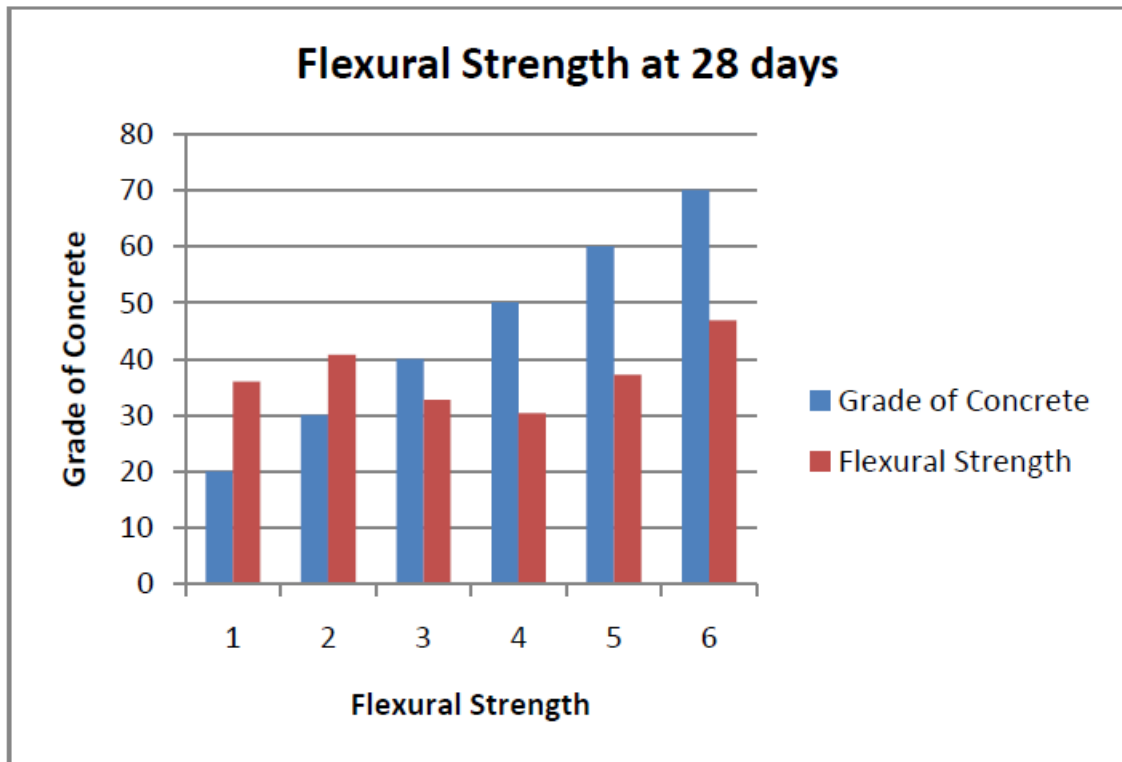


Fig 2. Variation of flexural strength at 28days

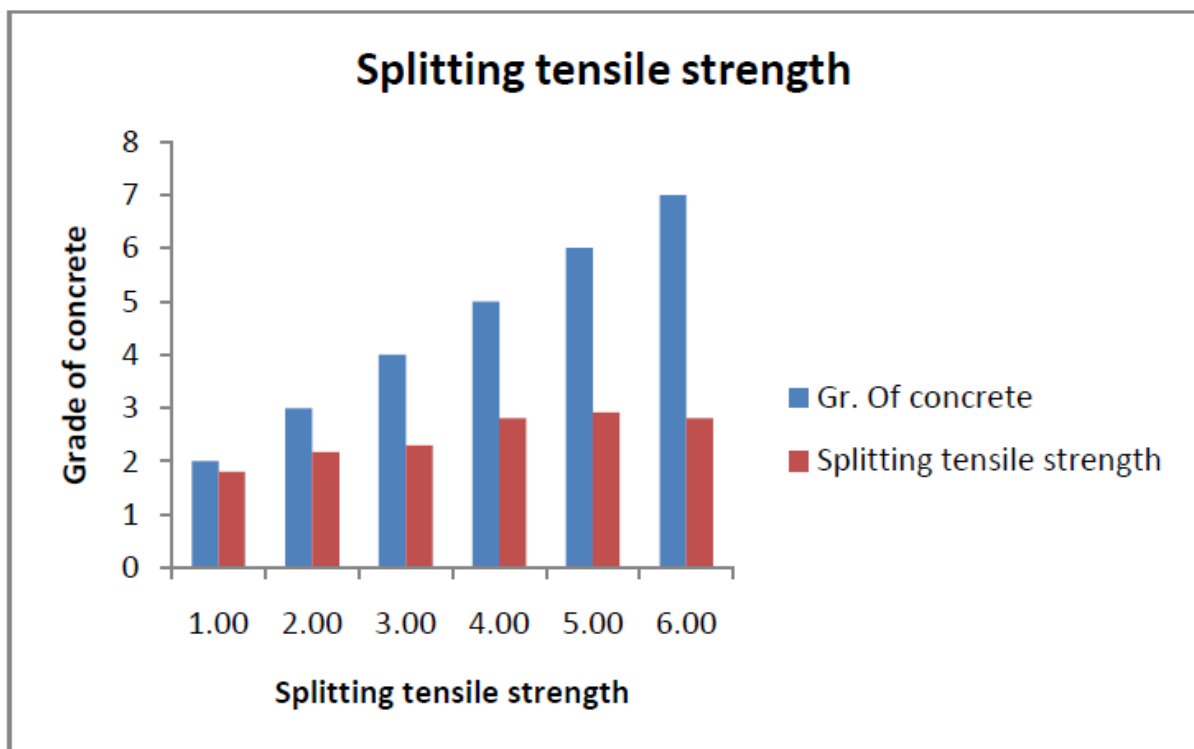


Fig3. Variation of splitting tensile strength at 28days